


PARAFLEX GREEN ROOF SYSTEM CONCRETE (non-nailable)

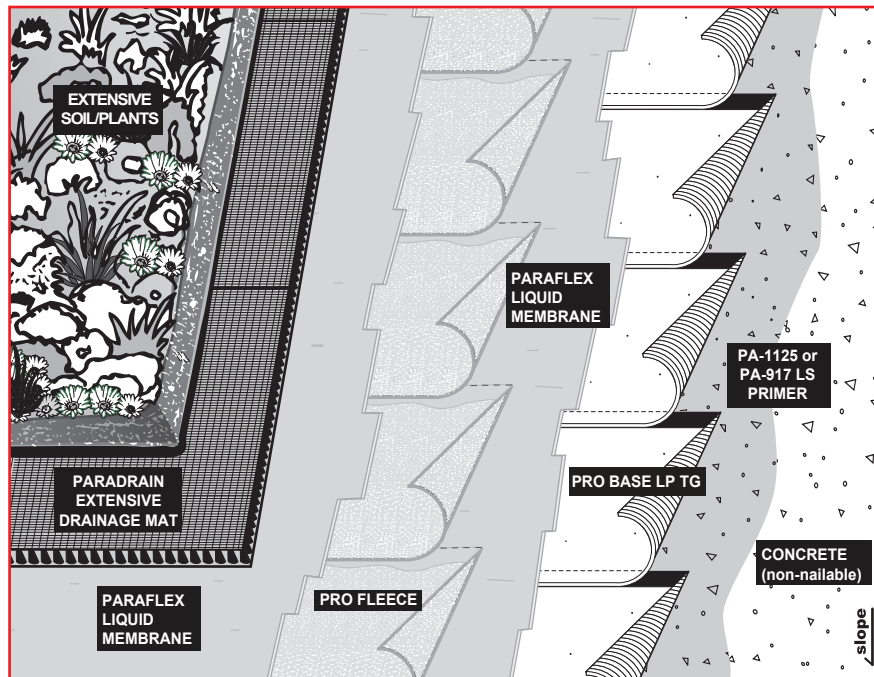

SLOPE	0" to 1" per foot*
MATERIALS	per 100 sq ft
PA-1125 OR PA-917 LS PRIMER	1 gal
PRO BASE LP TG	37 lbs
PARAFLEX LIQUID MEMBRANE	3.7 gal
PRO FLEECE	
PARAFLEX LIQUID MEMBRANE	1.9 gal
PARADRAIN EXTENSIVE DRAINAGE MAT	25 lbs
SOIL/PLANTS	

n.t.s.

Requirements and recommendations detailed in the Siplast catalog and Siplast long form specifications shall apply in addition to the following recommendations and specifications.

Application

1. Prime the entire deck using PA-1125 or PA-917 LS Primer and allow the primer to dry thoroughly.
2. Beginning at the low point of the roof, fully torch one ply of the Pro Base LP TG to the primed substrate, lapping sides and ends a minimum of 3 inches. Offset end laps a minimum of 3 feet.
3. Apply an even, generous base coat of Paraflex Liquid Membrane over the Pro Base LP TG surface using an approved stub roller at the minimum rate of 3.7 gallons per square.
4. While the previously applied Paraflex Liquid Membrane is still wet, install Pro Fleece reinforcement, embedding the fleece into the liquid material using a roller. Ensure that no air is trapped beneath the fleece. Lap the fleece a minimum 2 inches side and end, and apply an additional coat of liquid material between layers of overlapping fleece.
5. Immediately following embedment of the Pro Fleece reinforcement, apply an even, generous top coat of Paraflex Liquid Membrane at the minimum rate of 1.9 gallons per square, ensuring full saturation of the fleece.
6. Lay one layer of Paradrain Extensive Drainage Mat dry over the cured Paraflex Liquid Membrane surface.
7. Install soil and plants as specified.

Caution: Siplast recommends that all practices pertaining to NRCA CERTA guidelines be followed when torching methods are employed. This includes performing a fire watch following any torch applications. Always have approved fire-extinguishing equipment nearby.

Ref #: Ext-plants-Drain-mat-Pflex-PbaseLPTG-Concrete
Rev: 2.5.18